



Contents list available at IJRED website

Int. Journal of Renewable Energy Development (IJRED)

Journal homepage: <http://ejournal.undip.ac.id/index.php/ijred>



Synthesis of Trimethylolpropane Esters of Calophyllum Methyl Esters: Effect of Temperature and Molar Ratio

Yeti Widyawati^{1a}, Ani Suryani^{2a}, Muhammad Romli^{2b} and Sukardi^{2c}

¹⁾ Department of Chemical Engineering, Faculty of Technology Industry, University Jayabaya, Jakarta, Indonesia

^{2a,b,c)} Department of Agroindustrial Technology, Faculty of Agriculture Engineering and Technology, Bogor Agricultural University, Bogor, Indonesia

ABSTRACT: Trimethylolpropane esters were synthesized by transesterification of calophyllum methyl esters and trimethylolpropane using a calcium oxide as the catalyst. The results showed that the optimal reaction conditions (temperature: 130 °C, reaction time: 5 h, reactant molar ratio: 3.9:1, catalyst amount 3%w/w, and formed trimethylolpropane ester of 79.0% were obtained. The basic physicochemical properties of the trimethylolpropane esters were the following : kinematic viscosities of 56.40 cSt and 8.8 cSt at 40 °C and 100 °C, viscosity index 193, flash point 218 °C and pour point -3 °C. So Methyl esters of fatty acids of would calophyllum methyl ester is good raw material for the synthesis of lubricating oils.

Keywords: calophyllum methyl ester, transesterification, calcium oxide, trimethylolpropane esters.

Article History: Received March 12, 2014; Received in revised form July 23, 2014; Accepted August 10, 2014; Available online

How to Cite This Article: Widyawati, Y., Suryani, A., Romli, M. & Sukardi (2014) Synthesis of Trimethylolpropane Esters of Calophyllum Methyl Esters : Effect of Temperature and Molar Ratio. *Int. Journal of Renewable Energy Development*, 3(3), 188-192.

<http://dx.doi.org/10.14710/ijred.3.3.188-192>

1. Introduction

These last few years, the environmental issues and austerity of fossil raw materials require the development of environmentally friendly lubricants. Mineral oil-based lubricants are classified as non-renewable and environmentally-unfriendly materials (Salimon et al. 2010). In order to meet the demands of environmentally friendly lubricants and to use modern machines, it must be developed a synthetic lubricants.

Esters of vegetable oils are one of the recommended materials to be developed into a lubricant (Willing, 2001). Some vegetable oils used to make a synthetic lubricants are sunflower seed oil, castor, palm, rapeseed and soybean (Lathi PS & Mattiason 2007; Gryglewics et al. 2003). On the other hand, vegetable oil is environmentally friendly, because it is a renewable natural resource and can be degraded biologically.

There are several reasons to use vegetable oils or vegetable oil derivatives as biolubricants. Because as

much as 40% (Castro et al. 2006) of a lubricant can be lost to the environment, the inherent biodegradability of vegetable oils reduces their environmental impact. Other advantages include low volatility, superior lubricity and good anticorrosion properties (Doll et al. 2007; Metzger 2009).

However, vegetable oils also have the poor properties such as having a low oxidation stability and high pour point, both of which are critical factors for lubricants. The low oxidation resistance is caused by the carbon-carbon double bonds in the fatty acid chain and beta hydrogen on glycerol susceptible to oxygen assault. If there are two or more double bonds (polyunsaturated), the more easily oxidized. Meanwhile the presence of beta hydrogen will facilitate the breakup of triglycerides into acid and olefin. Transesterification is defined as the reaction (Leung et al. 2010) in which a triglyceride molecule reacts with three moles of methanol to result in glycerol and mixtures of fatty acid methyl esters. The transesterification of vegetable oil-derived methyl

*Corresponding author:

E-mail : widya_w21@yahoo.co.id

esters with polyols is essentially the reverse of the transesterification reaction, in which glycerol is replaced by a commercial polyol. The most significant advantage of using a polyol instead of glycerol is that the absence of beta hydrogens enhances the thermal stability of the lubricant at high temperatures by preventing self polymerization to form free fatty acids (Leung et al. 2010). Figure 1 show the chemical reaction between calophyllum methyl esters (CMEs) and trimethylolpropane (TMP).

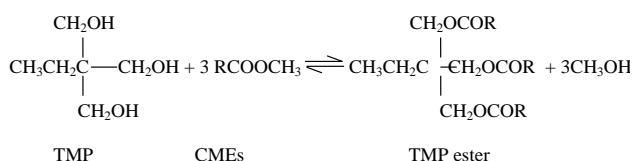


Fig. 1 reaction of TMP with CMEs

Previous studies reported on transesterification of palm oil methyl ester (POME) and palm kernel oil (PKO) with trimethylolpropane (TMP), which has been successfully converted into triesters of 98 % (Yunus 2003). Another study work reported using trimethylolpropane (TMP) and neopentylglycol (NPG) as a polyol with some vegetable oils such as olive oil, rapeseed oil and lard (Campanella et al. 2010). Uosukainen et al. (1998) describe the synthesis of trimethylolpropane esters of rapeseed oil methyl ester (ROME) using sodium methylate catalyst (0.5% w/w) were added to the reaction mixture. The reaction mixture is passed under pressure of 3.3 kPa for 8 hours. The effects of pressure, the molar ratio (TMP: ROME), reaction time, and reaction temperature investigated. The production of canola oil-based lubricant was studied transesterification with trimethylolpropane (TMP) using sodium methoxide as catalyst. They found the reaction conditions to obtain maximum yield of TMP trioleate. Canola derived biolubricant with TMP triester composition of 90.9% was obtained after 5 h (Sripada et al. 2013).

In the present study, calophyllum methyl esters is used to produce TMP esters. Calophyllum oil is semi-dried oil, rich in unsaturated fatty acids (oleic, lenoleic and lenolenic) which form 69.46% of total fatty acid composition of the oil. Presently, many studies on calophyllum oil shown that it has many potential for industrial application such as methyl esters. The objective of this study is to optimized the transesterification of calophyllum methyl esters with TMP to achieve the maximum production of TE. Through this process, TMP ester which is formed can be used as a basic material in the lubricant production.

2. Materials and Methods

2.1 Materials

Calophyllum methyl esters (CMEs), 2-ethyl-2-(hydroxymethyl)-1,3-propanediol and calcium oxide, was purchased from Merck Schuchardt. Other chemicals such as ethyl acetate and N, O-Bis (trimethylsilyl) trifluoroacetamide (BSTFA) were purchased from Sigma Aldrich.

2.2 Fractionation

Approximately 50% of the original calophyllum methyl esters (CMEs) were fractionated via vacuum distillation at temperatures of 170–180 °C under vacuum pressures of 2 mbar. The bottom product, which contains CMEs, was dried overnight in an oven at 110 °C to decrease the moisture content, and 200 g of it was used as the starting material in the synthesis of high oleic calophyllum oil based trimethylolpropane esters.

2.3 Transesterification

Transesterification reactions were performed in a 500 mL threeneck flask equipped with a thermometer, a sampling port and a reflux condenser. The condenser was connected to a vacuum line equipped with a relief valve, accumulator and vacuum trap. The reactor was filled with a known amount of TMP at a molar ratio of CMEs to TMP of 3.9 : 1, our now day study. The reactant was then heated and stirred with a magnetic stirrer in the temperature-controlled oil bath while under vacuum until the TMP melted at about 60 °C. Then the CMEs was added to a flask, and the mixture was heated to the operating temperature of 110 °C under vacuum pressure of 1–2 mbar. The calcium oxide catalyst was then added at a fixed 3% w/w based on the total mass of reactants. The vacuum was applied gradually to avoid spill over of the reaction materials. Samples were taken at specific time intervals, where each sample was collected in a small, capped vial and was immediately refrigerated at 2 °C for products analysis. Finally, the reaction mixture was cooled to room temperature and vacuum filtered to remove the catalyst and solid materials formed during the reaction.

2.4 Analysis

Analysis of TMP esters was performed on a HP 5890II gas chromatograph fitted with a capillary inlet system and flame ionization detector. The capillary column, HP INNOWAX, was 30 m long, with 0.25 mm i.d. and 0.25 µm film thickness. A split injection system 20:1 was used with helium carrier gas at head pressure of 0.6 atm. The column temperature was held at 50 °C throughout the entire 6 min run. Temperature programming was initiated at 50 °C at the rate of 10 °C min⁻¹ to reach a temperature of 250 °C. The inlet

temperature was 250 °C and the detector temperature was 280 °C. 1.0 mL of each prepared sample was automatically injected into the GC system.

2.5 Viscosity

Viscosity measurements were made at 40 and 100 °C using Cannon Fenske viscometer tubes in a Cannon Constant Temperature Viscosity Bath (Cannon Instrument Co., State College, PA). Viscosity and the viscosity index were calculated using ASTM methods D445 and D2270, respectively. All viscosity measurements were made in triplicate, and the average value was reported.

2.6 Pour point

Pour points were determined by ASTM method D97 with an accuracy of ± 3 °C using Automatic Pour Point Tester manufactured by Dott. Gianni Scavini & Co., Italy. All the runs were carried out in duplicate. Sample temperature was measured in 3 °C increments at the top of the sample until it stopped pouring.

2.7 Flash point

Flash point of the products was determined using Koehler Inc. apparatus as per ASTM D 93 method. The lowest temperature at which application of the test flame causes the vapour above the surface of the liquid to ignite is taken as the flash point of the product at ambient barometric pressure.

3. Result and Discussion

3.1 Effect of Temperature

The results show that the reaction temperature influences the formation of ME, DE and TE. The formation of TE increases with the increase of reaction temperature but drops slightly at 150°C (Figure 2). CMEs content in the reaction mixture also decreases during the reaction as it being transformed into ME, DE and TE. High temperature can cause the vaporization of CMEs from the reaction mixture and thus, encouraging forward reaction to form TE (Yunus 2003a). Vaporized CMEs mixture and produce a reversible reaction [8]. The aim of the study is to focus on TE production as it has good high temperature properties compared to ME and DE. The production of TE is high at 150 °C with few DE (5.80 %) and ME (0.40 %) formation in the final product. Although ME formation records the lowest (0.30%) at 130 °C, and DE (2.02%) at 110°C, both temperatures however record lower TE compare with when it was at 150 °C.

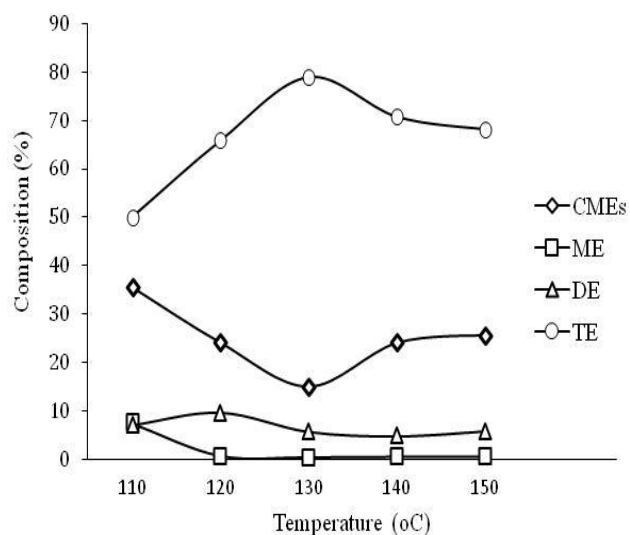


Fig. 2 Effect of temperature on transesterification of calophyllum methyl ester with TMP (TMP : CMEs = 1:3.9 ; catalyst 3%w/w, 5h)

3.2 Effect of Molar Ratio

One of the methods to promote forward reaction (fig. 1) is by using excess amount of one of the reactan. Since calophyllum methyl ester are relatively cheaper compared to trimethylolpropane, the reaction was subjected to excess methyl ester. The stoichiometri molar ratio between the calophyllum methyl ester and trimethylolpropane is 3 : 1. This is to ensure that the reaction was unconstrained by the effect of excess reactant. The investigation on the effect of CMEs : TMP molar ratio to conversion to TMP esters was carried out at 130 °C in 5 hours and catalyst was maintained at 3 % w/w in all experiment. The effect of molar ratio of TMP : CMEs on product composition is shown in Figure 3. The results are summarized in figure 3 which show that there is no significant effect of increasing molar ratio on the conversion of TMP ester. Slightly higher percentage of TMP esters was obtained at molar ratio of 1 : 3.7 and 1 : 3.9. However, the difference was so small (70.40 % and 71.80 %) that no conclusion could be withdrawn from the study.

3.3 Viscosity

The biolubricant product obtained from calophyllum methyl esters under the developed optimum synthesis conditions was evaluated for its lubrication properties. These properties were then compared with those of palm oil, canola (B. Napus) biodiesel-derived biolubricant, esterified rapessed oil and ISO VG 46. Table 1 shows a comparison of the lubrication properties of both biolubricants with reference to ISO VG 46 specifications. Determination of kinematic viscosity is important from the point of view of the ability of a lubricant to efficiently lubricate contact surfaces.

Kinematic viscosities were determined at 40°C and 100°C. Previous researchers reported kinematic viscosities at 40°C and 100°C of 52.40–10.20 cSt for TMP esters of palm oil (*E. gueneensis*) (Yunus et al., 2003b).

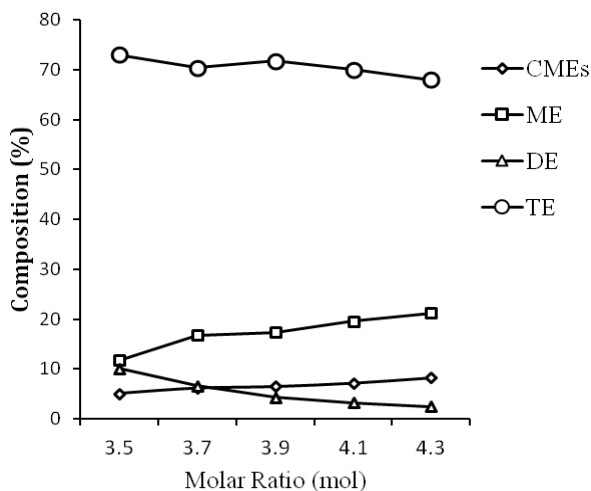


Figure 3 Effect of molar ratio on transesterification of calophyllum methyl ester with TMP (catalyst 3%w/w, 130 °C, 5h)

Similarly reported are kinematic viscosities at 40 °C and 100 °C of 40.5 cSt - 7.8 cSt for TMP ester canola oil (*B. Napus*) (Sripada 2013), respectively. Calophyllum methyl esters-derived biolubricant on the other hand was found to have kinematic viscosities of 56.40 cSt and 8.8 cSt at 40 °C and 100 °C respectively. ISO VG 46 is a standard specification for light gear oil lubricant. This specification was used as a reference for comparison. All the tribological properties of biolubricants were found to meet these specifications, except for the viscosity of calophyllum methyl esters-derived biolubricant, kinematic viscosities of 56.40 cSt at 40 °C, which was a bit higher than the recommended value of 41.4 cSt. This was due to the high monounsaturated and polyunsaturated in calophyllum methyl ester, which effectively resulted in higher viscosity. The viscosity of fluids tends to decrease as temperature is increased. VI quantifies the extent of change in the viscosity of lubricant with a change in temperature. Higher the VI, lesser is the change in viscosity of the lubricant with a change in temperature. A previous study reported the synthesis of TMP esters of palm oil (*E. gueneensis*) were found to exhibit high VI values of 167–187 (Yunus et al. 2003b). A VI value of 204 was obtained for polyol esters of canola oil (Sripada et al. 2013). TMP esters of C5–C18 fatty acids were observed to have VI values of 80–208 (Åkerman et al. 2011). Using the kinematic viscosity values at 40°C and 100°C, viscosity indices for calophyllum methyl ester derived biolubricants were calculated. Calophyllum methyl ester derived biolubricant was found to have high VI value of 193.

Table 1

Properties of calophyllum biolubricant at various temperatures and comparison with other plant based biolubricants.

Detail	Calophyllum oil biolubricant					Palm oil biolubricant ^a	Canola oil biolubricant ^b	Esterified rapeseed oil ^c	ISO VG 46 ^d
	110	120	130	140	150				
Temperatur (°C)	110	120	130	140	150				
Viscosity									
40 °C	35.28	54.43	56.40	56.87	56.93	52.40	40.5	35.34	>41.4
100 °C	7.68	8.49	8.80	8.70	8.32	10.20	7.80	7.99	>4.1
Viscosity Index (VI)	190	192	193	188	184	186	204	209.2	>90
Pour Point	-1	-2	-3	-1	-1	-5	-66	-15.5	-10
Flash Point	222	214	212	214	213	-	-	-	-

^a Yunus et al. 2003 ; ^b Sripada et al. 2013 ; ^c Gryglewicz et al. 2003 ; ^d Commercial lubricant

3.4 Pour Point

Low-temperature fluidity is the most important property for a lubricant to perform in extremely cold environments typical during the harsh winters of Canada, especially in Saskatchewan. A measure of the pour point values determine the cold flow properties of a lubricant. Pour point is the lowest temperature at which movement of the liquid is observed. A lot of work has been reported on the development of TMP triesters derived from palm (*E. gueneensis*) oil methyl esters (Yunus et al. 2003). They synthesized TMP lubricants from palm kernel (*E.gueneensis*) oil methyl esters, which had high pour points between +1°C and -1°C. In this work the pour point of the calophyllum methyl esters is -3 °C.

3.5 Flash Point

Flash point is used to determine the beginning of the lubricant will fire or flame arise while in the machine. The flash point of the calophyllum methyl ester is 212 °C indicating a low tendency to evaporation which fulfils one of the basic requirements of lubricants.

4. Conclusion

The transesterification of CMEs with TMP using calcium oxide as catalyst has successfully formed TMP esters with the percentage of TE (79%). Results of reaction duration: 5 hours, temperature 130 °C, molar ratio of CMEs: TMP is 3.9:1 and catalyst concentration: 3 % w/w (based on weight of reactan) are sufficient for the transesterification of TMP esters as biolubricant base stocks. In addition, the pour point of the product was observed of -3 °C, flash point is 212 °C and kinematic viscosities of 56.40 cSt and 8.8 cSt at 40 °C and 100 °C that resulting calophyllum TMP esters has a high potential for the production of lubricants.

Acknowledgments

The authors gratefully acknowledge to Directorate of Higher Education of Indonesia for the financial of Doctoral Research.

References

- Castro, W., Perez, J.M., Erhan, S.Z., Caputo, F. (2006) A study of the oxidation and wear properties of vegetable oils: soybean oil without additives. *J. Am. Oil Chem. Soc.* 83, 47–52.
- Doll, K.M., Sharma, B.K., Erhan, S.Z. (2007) Synthesis of branched methyl hydroxyl stearates including an ester from bio-based levulinic acid. *Ind. Eng. Chem. Res.* 46, 3513–3519.
- Lathi, S.P. & Mattiason, B. (2006) Green Approach for the Preparation of Biodegradable Lubricant Base Stock from Epoxidized Vegetable Oil. *Journal of Applied Catalysis B: Environmental* 69: 207-212.
- Leung, D.Y.C., Wu, X., Leung, M.K.H. (2010) A review of biodiesel production using catalyzed transesterification. *Appl. Energy* 87, 1083–1095.
- Gryglewicz, S., Piechocki, W., Gryglewicz, G. (2003) Preparation of polyol esters based on vegetable and animal fats. *Bioresour. Technol.* 87, 35–39.
- Phani K. Sripada, Rajesh V. Sharma, Ajay K. Dalai. (2013) Comparative study of tribological properties of trimethylolpropane-based biolubricants derived from methyl oleate and canola biodiesel. *Journal Industrial Crops and Products* 50, 95–103
- Salimon J, N. Salih, E. Yousif (2010) Improvement of pour point and oxidative stability of synthetic ester base stocks for biolubricant applications, *Arab. J. Chem.* 5, 193–200.
- Metzger, J.O. (2009) Fats and oils as renewable feedstock for chemistry. *Eur. Lipid Sci. Technol.* 111, 865–876.
- Nagendramma, P., Kaul, S. (2012) Development of ecofriendly/biodegradable lubricants: an overview. *Renew. Sustain. Energy Rev.* 16, 764–774.
- Uosukainen, E., Linko, Y.-Y., Lamsa, M., Tervakangas, T., Linko, P. (1998) Transesterification of trimethylolpropane and rapeseed oil methyl ester to environmentally acceptable lubricants. *J. Am. Oil Chem. Soc.* 75, 1557–1563.
- Willing A. (2001) Lubricants based on renewable resources – an environmentally compatible alternative to mineral oil products. *Chemosphere* ;43:89–98.
- Robiah, Y., Fakhru'l-Razi, A., Ooi, T.L., Iyuke, S.E dan Idris, A. 2003a. Development of Optimum Synthesis Method for Transesterification of Palm Oil Methyl Esters and Trimethylolpropane to Environmentally Acceptable Palm Oil-Based Lubricant. *Journal of Oil Palm Research* 15 (2): 35-41.
- Robiah, Y., Fakhru'l-Razi, A., Ooi, T.L., Iyuke, S.E dan Idris, A. 2003b. Preparation and Characterization of Trimethylolpropane Esters from Palm Kernel Methyl Esters. *Journal of Oil Palm Research* 15 (2): 42-49

Reproduced with permission of the copyright owner. Further reproduction prohibited without permission.